

**EKOTEKS LABORATUVAR ve GÖZETİM  
HİZMETLERİ A.Ş.**  
Esenyurt Firuzköy Bulvarı No:29 34325 Avcılar  
İstanbul/ TÜRKİYE

**TEST REPORT**  
DENEY RAPORU



AB-0583-T
22015797
06-22

**Customer name:** BRBEN TEKSTİL SAN. VE TİC.AŞ.  
**Address:** BAŞPINAR OSB MAH.OSB.2.BÖLGE 83207 NO'LU CAD.NO:2  
ŞEHİTKAMİL/GAZİANTEP  
**Buyer name:** -  
**Contact Person:** DERYA AKIN  
**Lot No/Parti No:** BRSCVR-001 Tip Pb (3,4,6)-B GALOSH  
**Article No:** BRSCVR2022/0048  
**Name and identity of test item:** White galosh (Claimed to be:2 Pieces White)  
**The date of receipt of test item:** 07.06.2022  
**Re-submitted/re-confirmation date:** -  
**Date of test:** 07.06.2022-09.06.2022  
**Remarks:** -  
**Sampling:** The results given in this report belong to the received sample by vendor.  
**End-Use:** -  
**Care Label:** Not Specified  
**Number of pages of the report:** 3

*The Turkish Accreditation Agency (TÜRKAK) is signatory to the multilateral agreements of the European co-operation for the Accreditation (EA) and of the International Laboratory Accreditation (ILAC) for the Mutual recognition of test reports.*

*EKOTEKS LABORATUVAR ve GÖZETİM HİZMETLERİ A.Ş. accredited by TÜRKAK under registration number [AB-0583-T] for ISO 17025:2017 as test laboratory.*

*The test and/or measurement results, the uncertainties (if applicable) with confidence probability and test methods are given on the following pages which are part of this report.*

Seal

Date  
09.06.2022

Customer Representative  
Serwin YURTSEVEN

Head of Testing Laboratory  
Sevim A. RAZAK  
09.06.2022

This report shall not be reproduced other than in full except with the permission of the laboratory.  
Testing reports without signature and seal are not valid.

EKOTEKS LABORATUVAR ve GÖZETİM  
HİZMETLERİ A.Ş.


AB-0583-T

22015797

06-22

REQUIRED TESTS	EVALUATION	COMMENTS
<b>PHYSICAL PROPERTIES TESTS</b>		
Seam Strength	-	Class 1
P: Pass F: Fail R: Refer to retailer technologist		
Test results were evaluated according to BS EN 14325:2018 "Protective clothing against chemicals-Test methods and performance classification of chemical protective clothing materials, seams, joins and assemblages" limit values		

**REMARK:** Original samples are kept for 3 months and all technical records are kept for 5 years unless otherwise specified. If requested, measurement uncertainty will be reported. But unless otherwise specified, measurement uncertainty is not considered while stating compliance with specification or limit values. The reported uncertainty is based on a standard uncertainty multiplied by a coverage factor  $k=2$ , providing a level of confidence of approximately 95 %. The declaration of conformity was given in accordance with the Simple Acceptance Decision Rule. Tests marked (\*) in this report are not included in the accreditation schedule.

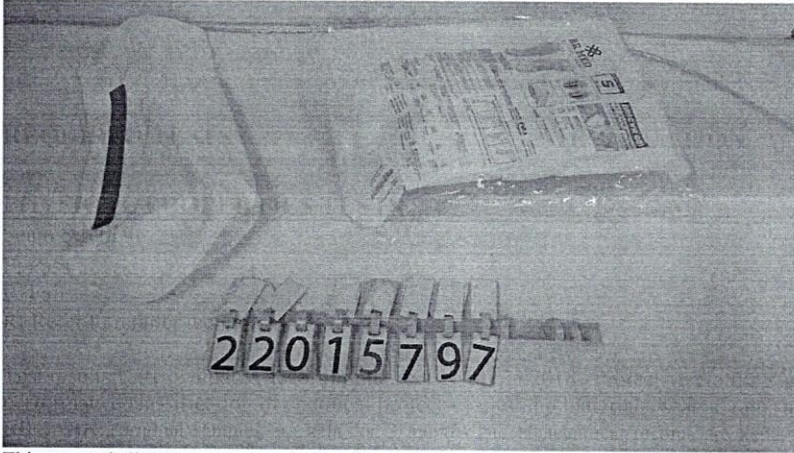

This report shall not be reproduced other than in full except with the permission of the laboratory.  
*Testing reports without signature and seal are not valid*

Gen.f136-2/03

AB-0583-T

22015797

06-22

## TEST RESULT

### SEAM STRENGTH(EN 14325(\*) CLAUSE 5.5)

#### SEAM STRENGTH ;ISO 13935-2: 2014

Jaw Speed: 50±5 mm/min, Gauge Length: 100 mm±1 mm.

Seam Type : 301. 100 % Polyester core-spun sewing-thread was used.

5kN. Load was applied.

The average results are given for width and length direction of five samples.

Performed in the conditioned room(20±2°C-65%±4)

	<u>Seam Strength (N)</u>	<u>Failure</u>	<u>CLASS</u>
Front seam	106.6	FTS	Class 1 (Classified according to the Table 13)
Back seam	121.1	FTS	
Sole seam	35.8	FTS	

FTS : Fabric Tear At The Seam

Table 13- Classification of Seam Strength

<u>CLASS</u>	<u>Seam strength</u>
6	>500 N
5	>300 N
4	>125 N
3	>75 N
2	>50 N
1	>30 N

Total uncertainty:±% 3,2